

## DURABILITY-BASED OPTIMAL DESIGN-METHODOLOGY FOR RC MEMEBERS IN CORROSIVE ENVIRONMENT

SAEID A. ALGHAMDI\*, SHAMSAD AHMAD AND ADAMU LAWAN

Department of Civil and Environmental Engineering, King Fahd University of Petroleum & Minerals  
P.O. Box 1896, Dhahran31261, Kingdom of Saudi Arabia

\*saghamdi@kfupm.edu.sa

shamsad@kfupm.edu.sa

adamul@kfupm.edu.sa

### ABSTRACT

As durability-based design of reinforced concrete (RC) structures in corrosive environments is *highly* influenced by chloride-induced corrosion of reinforcing steel bars, this paper first presents brief-outline of an experimental investigation recently carried out by the authors on a large number of reinforced concrete test-specimens subjected to several *scenarios* of chloride-driven reinforcement corrosion. Concrete specimens were prepared with cementitious material content of 350, 375 and 400 kg/m<sup>3</sup>, water-cementitious ratios of 0.4, 0.45 and 0.5, fine to total aggregate ratios of 0.35, 0.4 and 0.45, and cover thickness of 25, 37.5 and 50 mm. The specimens were then exposed to chloride solution of three different concentrations and were tested for determining corrosion-rate using electrochemical and gravimetric-weight loss methods. Numerical analysis of reinforcement-corrosion-rates (determined electrochemically and gravimetrically) was first used to determine statistical-correlation between corrosion rates obtained by the two methods. Then, the gravimetric reinforcement-corrosion-rate results were utilized for developing regression models for reinforcement corrosion rates in terms of concrete quality parameters, concrete cover-thickness and chloride concentration. The regression models obtained for reinforcement-corrosion-rates were adapted within an *automated* analysis-design-methodology using *Microsoft Excel* solver for durability-based optimal design of RC members subjected to specified-chloride-exposure corrosive-environments. Sample results obtained from the design-methodology outlined in this paper are summarized for selected case-studies of RC-beams and columns.

### 1. INTRODUCTION

As regards the durability of reinforced concrete structures under known chloride-exposure conditions, chloride-ions driven corrosion of reinforcing steel is known to be a major design-problem for RC structures. And while quality of concrete and cover thickness play a major role in initiation and progress of reinforcement corrosion, it is particularly noted that, deterioration of RC structures in a corrosive-environment (taking coastal region of Saudi Arabia as an example) is mainly attributed to: (i) extreme environmental conditions, (ii) substandard quality of construction materials and/or (iii) inadequate construction practices. Environmental conditions of the area are characterized by wide variations in daily and seasonal temperatures (Saricimen, 1993). Such variations in day to night temperature lead to formation of micro-cracks in concrete-matrix which accelerates diffusion of aggressive species, such as

chlorides, to surface of steel bars. The conditions required for initiating corrosion of reinforcing steel are satisfied, and the resulting corrosion-products of confined steel-bars would produce expansive forces of magnitude that may exceed by far the tensile strength of concrete matrix (Dyer, 2014). Therefore, reinforced concrete structures in such environments should be designed to satisfy both durability and strength requirement (Shameem *et al.*, 1995; Alghamdi and Ahmad, 2010).

For carrying out structural durability-based design of RC-members, the following two effects of degradations in concrete and steel should therefore be considered:

- i) loss of concrete cover leading to reduced cross-sectional area of the concrete due to surface deterioration; and
- ii) loss of steel cross-sectional area, steel-to concrete bond, and loss of concrete cover due to expansive-forces resulting from reinforcement corrosion-products.

For RC-structures under aggressive-exposure conditions, excluding frost attack, a model for evaluating the rate of deterioration of surface concrete  $C_r$  (mm/year; being the rate of loss of structurally effective concrete), a model was previously given (Pihlajavaara, 1994) as follows in Eq. (1)

$$C_r = \frac{c_{env}c_{cur}}{f_{ck}^{3.3}} \quad (1)$$

where:

- $c_{env}$  = environmental coefficient;
- $c_{cur}$  = curing coefficient; and
- $f_{ck}$  = characteristic cubic compressive strength of concrete at 28 days (MPa).

In the Gulf region (within latitude  $10^0 - 30^0$ ), values of  $c_{env}$  were assumed to be within the range of  $10$  to  $500 \times 10^3$  (Pihlajavaara, 1994), and the curing coefficient,  $c_{cur}$ , may be calculated by using the following equation (Vesikari, 1995).

$$C_{cur} = \frac{1}{0.85 + 0.17 \log_{10}(d)} \quad (2)$$

where:  $d$  = the curing time (days).

Loss-rate of structurally effective concrete  $C_r$ , is calculated by using Eq. (1), and the reduced cross-sectional area of concrete, at any exposure time  $t$ , may be calculated by using  $c'(t)$  from Eq. (3):

$$C'(t) = C_r(t) \quad (3)$$

The cross-section residual dimensions (*namely*: width  $b'(t)$ , and depth  $h'(t)$ ) for a concrete member at any exposure time  $t$ , may be calculated using Eqs. (4) and (5)

$$b'(t) = b_o - 2c'(t) \quad (4)$$

$$h'(t) = h_o - 2c'(t) \quad (5)$$

where:  $b_o$  and  $h_o$  are respectively initial width and depth of a given RC-member.

Value of corrosion penetration rate  $P_r$ , is determined using Eq. (6),

$$P_r = \frac{W}{F \gamma_{st}} I_{corr} \quad (6)$$

where:

$$F = 96500 \text{ A} \cdot \text{s}; W = 27.93 \text{ g}$$

$$\gamma_{st} = 7.85 \text{ g} / \text{cm}^3$$

The loss of steel-rebar diameter  $d'(t)$  leading to a reduced cross-sectional area of steel at any exposure time  $t$  is calculated using Eq. (7).

$$d'(t) = P_r(t) \quad (7)$$

Then a reduced diameter  $D'(t)$  of rebar at any exposure time  $t$  is given by Eq. (8),

$$D'(t) = D_o - 2d'(t) \quad (8)$$

where  $D_o$  is the initial diameter of rebar.

The main objectives of this research work are to:

- a) determine reinforcement corrosion rate using electrochemical and gravimetric techniques on a large number of concrete specimens designed with specified combinations of design variables *including* water-cementitious material ratio (w/c), cementitious material content, fine to total aggregate ratio and cover thickness;
- b) determine correlation between electrochemically and gravimetrically measured reinforcement corrosion rates; and
- c) outline and demonstrate utilization of a methodology for durability-based design of RC members in a specified corrosive environments

## 2.0 EXPERIMENTAL PROGRAM

### 2.1 Construction Materials and Properties

This research study is based on type I Normal Portland Cement used with 8% Silica Fume added to all concrete mixtures. All concrete test-specimens were prepared with aggregates obtained from two different sources located in the eastern and western regions of the Kingdom (*namely*: Abu Hadriyah quarries and Taif quarries), referred to hereafter as H-type and T-type aggregates, samples of which are shown in Figure 1. The T-type aggregate is composed mainly of coarse-grained *silicate minerals* (such as: quartz and feldspar) known to produce weaker bonds with cement paste than the H-type (mainly *calcareous* rocks, such limestone and dolomite). And with the established influence of aggregates-type, based on *mineralogical* and *petrographic* characteristics (Bérubé, 2001), on durability of concrete matrix and RC structures in corrosive-environments (Saricimen, 1993), the characteristics of the two types of coarse aggregates were previously studied (Alghamdi and Ahmad, 2010). Development of micro-cracking at materials' interface-lines and harmful levels concrete-permeability (consequentially undermining structural durability) are *invariably* caused by particular types

of coarse-aggregates. As such coarse-aggregates properties were identified as most-influential on thermal and stiffness characteristics and incompatibilities between concrete-matrix constituents. And for the purpose of this research work, specific gravity and water absorption of used coarse aggregates were determined, and abrasion test results were obtained (respectively, in accordance with ASTM C128 and ASTM C131) and the results are listed in Table 1. The specific gravity and absorption of fine aggregate were found to be 2.6 and 0.57%, respectively. Super-plasticizer was added during mix-design with low water-cement ratio, in order to enhance workability of concrete mixtures.

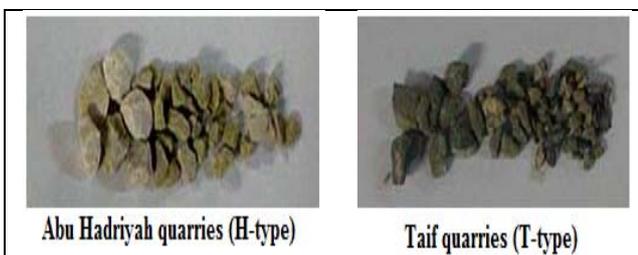


Figure 1: Samples of the two types of coarse aggregates used

Table 1: Coarse aggregates properties

Aggregate source	Specific gravity	Water absorption (%)	Abrasion loss (%)
Abu Hadriyah (H)	2.55	1.10	28.86
Taif (T)	2.88	2.01	37.84

## 2.2 Test specimens and concrete mix design

Steel bars of diameter 16 mm were centrally-placed in each one of 486 cylindrical concrete test specimens with height of 150 mm, diameters of 66 mm, 91 mm and 116 mm, and with three different cover thicknesses of 25 mm, 37.5 mm and 50 mm. Test specimens were prepared to evaluate corrosion rate and epoxy coating was applied to steel bar at bottom-end and at interface-end extending from within top-end of concrete-matrix upwards as shown in Figure 2.

Absolute volume method was employed for the concrete mix-design. The groups of water-cementitious ratio, cementitious material content and fine to total aggregate ratio used to prepare the specimens were respectively ( $R_{w/c}$ : 0.4, 0.45 and 0.5), ( $C_c$ : 350, 375 and 400 kg/m<sup>3</sup>), and ( $R_{F/T}$ : 0.35, 0.4 and 0.45). Three chloride concentrations of 3%, 7% and 12% were used to simulate corrosive conditions. And in order to obtain homogenous concrete matrix having uniform consistency without

segregation, all constituents were uniformly mixed together, with the addition of potable water and super-plasticizer, using a revolving drum-type mixer. Test specimens were de-molded after 24 hours of concrete casting and specimens were then cured for a period of 28 days in water tanks under laboratory conditions, and were subsequently partly submerged in chloride solutions to allow corrosion to take place. Samples of test specimens exposed to a chloride solution are shown in Figure 3.

## 2.3 Experimental program

### 2.3.1 Linear polarization resistance method (LPRM)

The LPRM was employed to measure the corrosion current density ( $I_{corr}$ ) using PARSTAT 2273 potentiostat equipment (PowerCORR, 2001). As a means of evaluating the instantaneous corrosion rate of reinforcing steel in concrete, the technique is applied to measure corrosion current density using a three-electrode system comprising of: i) reference electrode; ii) counter electrode (steel plate) which was connected to the respective terminals of the potentiostat; and iii) steel reinforcement in the concrete specimen (often known as the *working electrode*) polarized to  $\pm 20$  mV from its equilibrium (*rest*) potential at a perturbation scan rate of 0.166 mV per second.

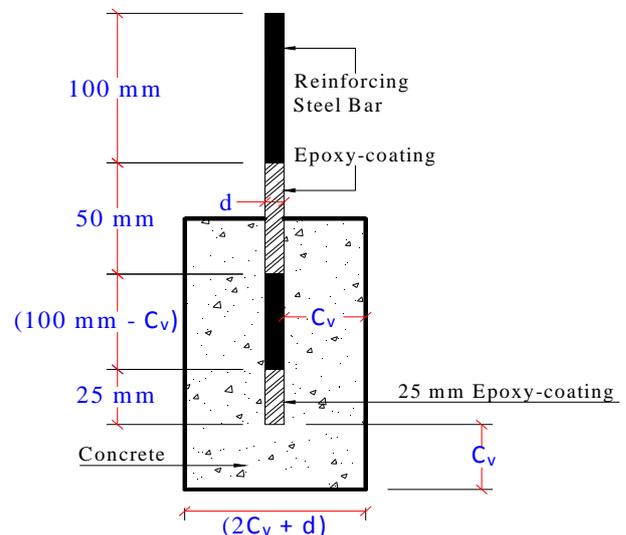


Figure 2: Details of typical test specimen.



Figure 3: Sample of test-specimens exposed to chloride solution.

Steel reinforcement was then polarized after an appropriate *initial delay* of about 1 minute, and the linear polarization resistance  $R_p$  ( $k\Omega \text{ cm}^2$ ) was determined from the slope of the applied potential *versus* measured current plot. Corrosion current density  $I_{corr}$  ( $\mu A/\text{cm}^2$ ) is then calculated using eq. (9)

$$I_{corr} = \frac{B}{R_p} \quad (9)$$

where:

$$B = \frac{\beta_a \beta_c}{(\beta_a + \beta_c)} \quad (\text{with: } \beta_a \text{ and } \beta_c \text{ being, respectively, anodic and cathodic Tafel constants);}$$

$$R_p = \text{polarization resistance } (k\Omega \cdot \text{cm}^2).$$

A Tafel-plot is normally utilized to find Tafel constants, but when the plot is *not* available,  $B$ -values of 26 mV and 52 mV have been recommended (Al-Tayyib and Khan, 1988) for steel-bars in *active* and *passive* states, respectively. In this work a value of 26 mV was used

### 2.3.2 Gravimetric weight loss method (GWLM)

Following corrosion rate measurements using LPRM, all concrete samples were then broken for determination of corrosion rate by gravimetric weight loss method. Preparation, cleaning and estimation of weight loss were done in accordance with ASTM G1-03. The cleaning solution was prepared by adding 20 g of *antimony trioxide* and 50 g of *stannous chloride* in 1000 ml of hydrochloric acid. Samples of corroded steel bars obtained from test specimens before and after cleaning are shown in Figure 4.

The weight loss  $\Delta W$  was calculated as:

$$\Delta W = W_i - W_f \quad (10)$$

where:  $W_i$  = initial weight of the bars before corrosion (g), and  $W_f$  = weight of the bars after cleaning all rust products (g).

Then the corrosion penetration rate,  $P_r$  ( $\mu\text{m}/\text{year}$ ) was determined using Eq. (11):

$$P_r = \frac{1.116 \times 10^7 \times \Delta W}{A \times T} \quad (11)$$

in which:  $A$  = exposed surface area of rebar ( $\text{cm}^2$ ); and  $T$  = exposure time (hours).

Corrosion penetration rate  $P_r$  was converted to corrosion current density  $I_{corr}$  using a simplified relationship (Alghamdi and Ahmad, 2010) given by Eq. (12):

$$I_{corr} = \frac{P_r}{11.7} \quad (12)$$



Figure 4: Samples of corroded rebars before and after cleaning.

## 3.0 RESULTS AND DISCUSSION

### 3.1 Correlation between $I_{corr,g}$ and $I_{corr,e}$

Values of reinforcement-corrosion-rate measured in terms of corrosion current density using electrochemical and gravimetric methods (designated as  $I_{corr,e}$  and  $I_{corr,g}$ , respectively) obtained for all the test specimens were analyzed with full details presented previously (Alghamdi and Ahmad, 2010). A close inspection of results obtained indicates that effects of aggregate-type, cover-thickness and chloride-concentration on correlation between the corrosion current density determined by LPRM and GWLM are practically insignificant. Hence, a single plot of corrosion current density values determined by LPRM against corresponding corrosion current-density values determined by GWLM for all 486 test-specimens is shown in Figure 5 in which good correlation between  $I_{corr,g}$  and  $I_{corr,e}$  values are clearly reflected by correlation-coefficient value nearly equal to 0.96. Correlation analysis also indicates that value of gravimetric corrosion current density is, on average, nearly equal to 86% of values of electrochemical corrosion current density.

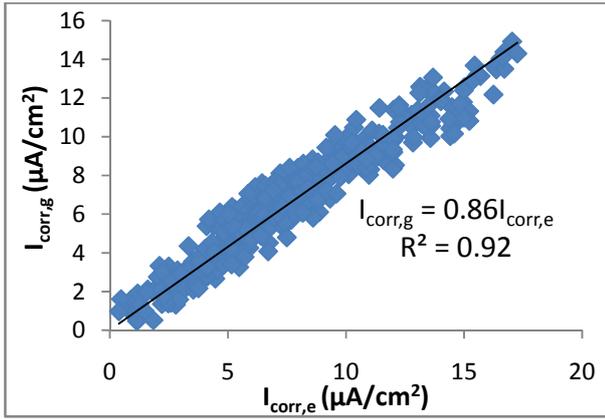


Figure 5: Correlation of  $I_{corr,g}$  to  $I_{corr,e}$  for all test specimens.

### 3.2 Regression models for corrosion rate

Since gravimetrically-computed reinforcement corrosion rates were found to be more accurate and reliable, the models for predicting corrosion current density in terms of water-cementitious materials ratio (w/cm ratio), fine to total aggregate ratio, cover thickness, cementitious materials content and chloride concentration were developed using Minitab software (Alghamdi and Ahmad, 2010), separately for the two aggregate-types using gravimetric data. A linear-type regression model was selected considering the linear variation of corrosion rate with major design factors (including:  $R_{w/c}$ ,  $C_c$ ,  $R_{F/T}$ ,  $C_L$ , and  $C_v$ ) affecting corrosion rate. Regression models for corrosion current density obtained for both types of aggregates are presented in Table 2.

Table 2: Regression models for corrosion current density

Aggregate Type	Regression models	R <sup>2</sup>
H	$I_{corr} = -13 + 34.4 R_{w/c}$	0.82
	$+ 0.024 C_c$	
	$+ 3.83 R_{F/T}$	
	$+ 0.097 C_L$	
	$- 0.181 C_v$	
T	$I_{corr} = -18.4 + 43.8 R_{w/c}$	0.94
	$+ 0.03 C_c$	
	$+ 4.77 R_{F/T}$	
	$+ 0.12 C_L$	
	$- 0.203 C_v$	

### 3.3 Durability-based optimal design methodology

Durability-based design of typical RC members can be performed by utilizing regression models (outlined in the previous section) for prediction of corrosion current density. For a specified design service-life (Sarja and Vesikari, 1996), the minimum value of corrosion current density  $I_{corr}$  were used to

determine loss of steel rebar due to corrosion and was then utilized within a durability-based optimal structural design search-methodology.

The following *five-step design-procedure* (Alghamdi and Ahmad, 2010), was utilized for durability-based design RC beams and columns:

- i) *Microsoft Excel solver* is used to determine optimum values of water to cementitious material ratio ( $R_{w/c}$ ), cementitious material content ( $C_c$ ), concrete cover ( $C_v$ ), fine to total aggregate ratio ( $R_{F/T}$ ) corresponding to minimum corrosion current density  $I_{corr,g}$  for specified chloride concentration using the models developed for  $I_{corr,g}$ .
- ii) Compressive strength  $f'_c$  and elastic modulus  $E_c$  of concrete are determined using optimum values of  $R_{w/c}$ ,  $C_c$  and  $R_{F/T}$  in the following models (Adamu, 2011).
$$f'_c = -61.24 - 0.056 C_c - 19.87 \text{Exp}(2.083 R_{w/c}) + 183.45 R_{F/T}^{0.119} \quad (14)$$

$$E_c = -49.10 - 0.0048 C_c - 13.23 \text{Exp}(2.083 R_{w/c}) + 145.68 R_{F/T}^{0.106} \quad (15)$$
- iii) Loss-rates of concrete cover and rebar diameter are determined from Eqs. 3 and 7 using the data obtained in steps (i) and (ii) given above. A preliminary section is then specified for a given structural member and the residual dimensions of cross-section and rebar diameter are determined.
- iv) A durability-based structural-design of RC-concrete members is performed using design-information obtained in step (iii) given above.
- v) Adequacy of final cross-section and rebar diameter is checked against prescribed design requirements.

The design methodology for carrying out durability-based optimal structural-designs is outlined in the flowcharts shown in Figures 6 and 7 for design of RC beams and columns, respectively. The design-procedure was implemented in two Microsoft Excel programs (designated as: RC\_B\_DDesign and RC\_C\_DDesign) suitable for automated design of RC beams and columns, respectively, in corrosive environment. Sample values of typical input and output results obtained for durability-based design of typical design case-studies for RC beams and columns are summarized in Table 3 and 4, respectively.

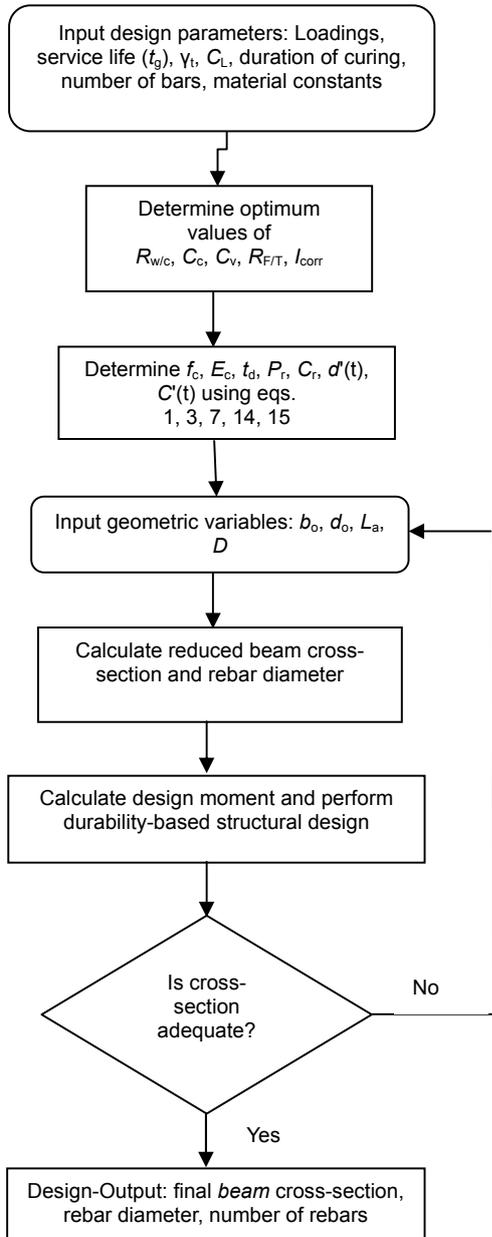


Figure 6: Flowchart for durability-based design of RC beam.

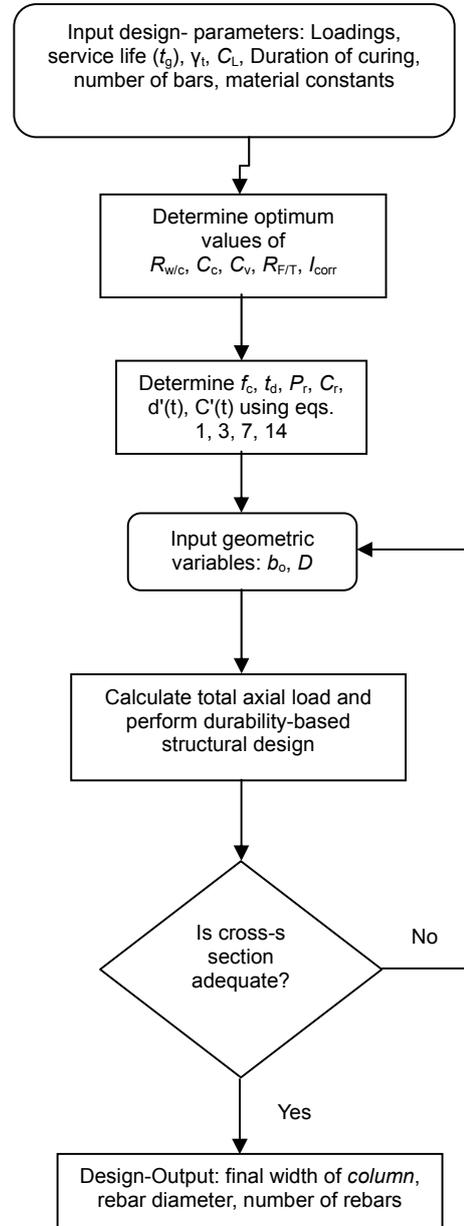


Figure 7: Flowchart for durability-based design of RC column.

#### 4.0 CONCLUSIONS

In this research study, 486 concrete specimens with centrally placed reinforcing steel bar were subjected to experimental conditions for chloride-induced corrosion. The study was conducted to develop correlation relationship between corrosion current density values determined based on data compiled from linear-polarization-resistance method (LPRM) and gravimetric-weight-loss method (GWLM). Reliable models for prediction of reinforcement corrosion rate were also developed and utilized within an automated methodology for durability-based design of RC beams and columns. And to demonstrate utilization of the design-methodology, the results obtained from design case-studies of sample RC beams and columns are summarized and presented in this paper.

**Table 3:** Sample design-results obtained by RC\_B\_DDesign program for durability-based optimal design of RC beam

S/N	Input design values		Optimal design values		
	Target life, $t_g$ (years)	$C_L$ (%)	Beam-width $b_{optim}$ (mm)	Beam-depth, $d_{optim}$ (mm)	Bar diameter $D_{optim} = D + \Delta D$ (mm)
1	40	3	200	528	18.11
2		7	200	403	20.71
3		12	200	310	23.59
4	50	3	225	436	19.60
5		7	225	331	22.49
6		12	225	300	23.63
7	70	3	225	345	22.04
8		7	225	300	23.63
9		12	225	300	23.63

\* **Note:** Length = 3 m; dead-load = 40 kN/m; live-load 12 kN/m;  $\Delta D$  = Additional increment to steel bar diameter to off-set corrosion effect.

**Table 4:** Sample design-results obtained by RC\_C\_DDesign for durability-based optimal design of RC column

S/N	Input design values		Optimal design values	
	Target service life, $t_g$ (years)	$C_L$ (%)	Column width, $b_{optim}$ (mm)	Bar diameter, $D_{optim} = D + \Delta D$ (mm)
1	40	3	150	15.76
2		7	150	15.76
3		12	150	15.76
4	50	3	150	15.76
5		7	150	15.76
6		12	170	15.76
7	70	3	150	15.76
8		7	268	15.76
9		12	650	15.76

\* **Note:** Dead-load = 100 kN; live-load 120 kN

#### Acknowledgment

This research work was conducted and completed under research-grant (ID KACST AT-23-21) provided by the King Abdulaziz City for Science & Technology (KACST; Riyadh-KSA). The authors acknowledge with appreciation, the financial and logistical supports provided by both KACST and the Department of Civil and Environmental Engineering at King Fahd University of Petroleum and Minerals (KFUPM-Dhahran).

#### REFERENCES

- Adamu L., 2011. Electrochemical and gravimetric studies towards service-life prediction and durability-based design of RC structures in corrosive environments. MSc. thesis submitted to the Deanship of Graduate Studies, King Fahd University of Petroleum and Minerals, Dhahran.
- Alghamdi S.A., Ahmad S., 2010. Multi-criterion optimal designs of RC beams and columns: experimental and analytical studies. Final Report, Research Project AT-23-21.
- Ahmad S., Alghamdi S.A., 2014. A statistical approach to optimizing concrete mixture design. The Scientific World Journal, Article ID 561539, 7 pages.
- Al-Tayyib, A.J., Khan, M.S., 1988. Corrosion rate measurement of reinforcing steel in concrete by electrochemical techniques. ACI Materials J., May-June, 171-177.
- ASTM C 128-07a. *Standard test method for density, relative density (Specific Gravity) and absorption of fine aggregate*. ASTM, West Conshohocken, Pa.
- ASTM C131, 2006. *Standard test method for resistance to degradation of small-size coarse*

- aggregate by abrasion and impact in the Los Angeles Machine. ASTM, West Conshohocken, Pa.
- ASTM G 1-03., 2003. Standard practice for preparing, cleaning, and evaluating corrosion test specimens. ASTM, West Conshohocken, PA.
- Bérubé, M-A., 2001. The mineralogical and petrographic analysis of concrete aggregates. *J. Mineralogy Overview (JMO)*: 53 (12), 45-47.
- Dyer, T., 2014. Concrete durability. CC Press, Taylor & Francis Group, Boca Raton, Florida.
- MINITAB, 2000. Statistical package. Release 13 for Windows 95 and 98.
- Pihlajavaara, S.E. 1994. Contributions for the development of the estimation of long-term performance and service-life of concrete. Report 3, Articles 49, Helsinki University of Technology, Faculty of Civil Engineering and Surveying, Espoo. 1 - 26.
- PowerCORR, 2001. User's manual, Corrosion Measurement Software. Princeton Applied Research, USA.
- Saricimen H., 1993. Concrete durability problems in the arabian gulf region - A review. Proceedings, Fourth international conference deterioration and repair of R.C. in the Arabian Gulf, Bahrain.
- Sarja, A. and Vesikari, E., 1996. Durability design of concrete structures. Report of RILEM Technical Committee, E & FN Spon.
- Shameem M., Maslehuddin M., Saricimen H., Al-Mana A. I., 1995. Extending the life of reinforced concrete structures in the Arabian Gulf environment. Proceedings, Structural Faults and Repairs conference, London, 115-126.
- Vesikari, E., 1995. Service-life design of concrete structures. *RIL 183-4.9, Association of Finnish Civil Engineers*, RIL, Helsinki.